

Understanding the Surface Structure of LiMn_2O_4 Spinel Cathodes with Aberration-Corrected HAADF STEM and EELS

C. Amos¹, M.A. Roldan^{2,3}, M. Varela^{2,3}, J.B. Goodenough¹, P.J. Ferreira¹

¹. Materials Science and Engineering Program, The University of Texas at Austin, Austin, TX, USA.

². The STEM Group, Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, TN, USA.

³. Universidad Complutense de Madrid, Madrid, Spain.

As global energy consumption continues to rise, the importance of energy storage becomes increasingly important. Energy density, rate-capability, and cyclability must continually improve. This constant struggle for advancement is seen most easily in the high-density, electrical energy storage market, which is dominated by lithium-ion batteries. One of the most promising chemistries in lithium-ion batteries is LiMn_2O_4 (LMO), a spinel cathode material which has the advantage of both a high energy density and a high rate capability, but this chemistry is plagued with cyclability problems. In the LMO system the main contributor to cycling degradation is the Mn disproportionation reaction ($2\text{Mn}^{3+} = \text{Mn}^{2+} + \text{Mn}^{4+}$) which creates soluble Mn^{2+} that is lost to solution. This loss of active material from LMO leads to capacity degradation. In order to understand exactly how LMO loses active material from its surface, it is crucial to determine the surface's atomic structure. This is because the surface structure dictates how the electrolyte will interact with the cathode.

In this paper, we use a combination of high-angle annular dark-field (HAADF) aberration-corrected scanning transmission electron microscopy (STEM) and electron energy loss spectroscopy (EELS) to identify the atomic surface structure and composition of LMO. We confirm the underlying spinel structure and for the first time we find, in as-processed LMO, a surface structure composed of Mn_3O_4 and a lithium-rich $\text{Li}_{1+x}\text{Mn}_2\text{O}_4$ subsurface layer which occurs as a result of the surface reconstruction. These conclusions are reached based on Mn oxidation state and oxygen content mapping with EELS as well as structural identification with HAADF STEM and STEM simulations. The presence of Mn^{2+} at the surface provides direct evidence of the Mn disproportionation reaction which has only been indirectly proven, until now. We have also identified that oxygen loss is the mechanism by which the surface reconstruction occurs. This solid understanding of the interface between the cathode and the electrolyte gives us insight into mitigating the undesired surface reactions that occur in the LMO system. Through these pioneering experiments we have gained a deeper understanding of interfacial phenomena in LMO which will be of central importance for all types of lithium-ion chemistries and continue to push the evolution of portable, electrical energy storage.

[1] This work was supported by a NASA Office of the Chief Technologist's Space Technology Research Fellowship. We acknowledge the use of the aberration-corrected ARM 200F STEM at the University of Texas at San Antonio, a facility supported by a grant from the National Institute on Minority Health and Health Disparities (G12MD007591) from the National Institutes of Health. J.B. Goodenough thanks the Robert M. Welch Foundation Grant F-1066 for financial support. Research at ORNL (MV) supported by the US Department of Energy, Office of Science, Basic Energy Sciences, Materials Sciences and Engineering Division and through a user project supported by ORNL's Center for Nanophase Materials Sciences (CNMS), which is sponsored by the Scientific User Facilities

Division, Office of Basic Energy Sciences, U.S. Department of Energy. Research at UCM (MR) was supported by the ERC starting Investigator Award, grant #239739 STEMOX.

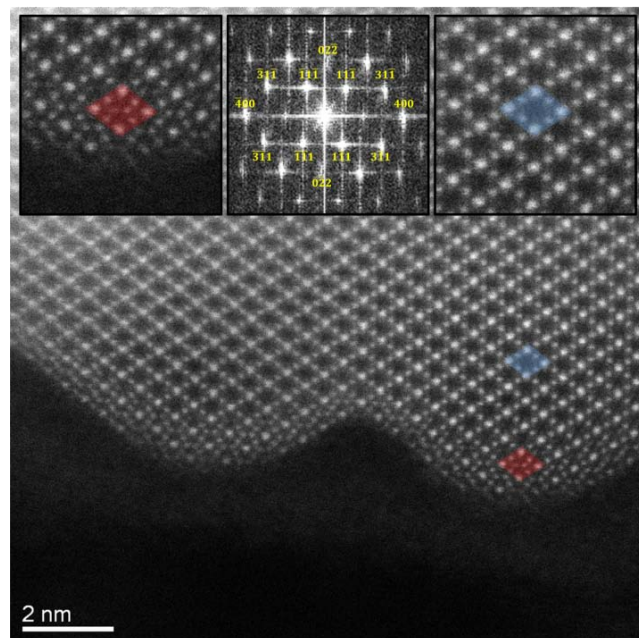


Figure 1. HAADF STEM image of LMO viewed along the [110] zone axis. LMO diamonds (blue) are found in the bulk while Mn_3O_4 (red diamond) is visible at the surface. The insets in the image show a higher magnification of the bulk (top right) and surface (top left). An FFT of the full image (top center) is included to indicate the crystal orientation.

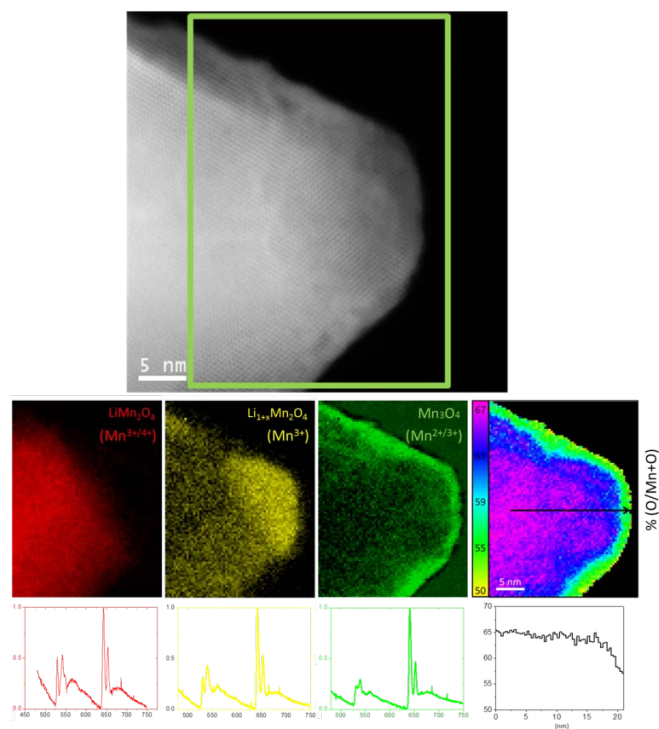


Figure 2. HAADF STEM image of an LMO particle (top). The green rectangle in the STEM image shows the area from where an EELS spectrum image was acquired. The colored maps (red, yellow, and green) and corresponding colored spectra below each image, represent the location of different Mn valence states within the nanoparticle. The oxygen content relative to Mn extracted from the O-K and Mn $L_{2,3}$ edges is shown (middle right). The black arrow shows where the relative oxygen percentage (bottom right) was extracted. The ratio is determined by the number of oxygen atoms to the total number of atoms in the sample.